arXiv:cond-mat/9702086v1 [cond-mat.mtrl-sci] 10 Feb 1997

Non–Nominal Value of the Dynamical Effective Charge in Alkaline–Earth Oxides

M. Posternak† and A. Baldereschi†

Institut de Physique Appliquée, Ecole Polytechnique Fédérale, PHB Ecublens, CH–1015 Lausanne, Switzerland

H. Krakauer

Department of Physics, College of William and Mary, Williamsburg, Virginia 23187–8795

R. Resta

INFM–Dipartimento di Fisica Teorica, Università di Trieste, Strada Costiera 11, I–34014 Trieste, Italy

(February 1, 2008)

Abstract

We calculate *ab–initio* the electronic states and the Born dynamical charge Z^* of the alkaline–earth oxides in the local–density approximation. We investigate the trend of increasing Z^* values through the series, using band–by–band decompositions and computational experiments performed on fake materials with artificially–modified covalence. The deviations of Z^* from the nominal value 2 are due to the increasing interaction between O $2p$ orbitals and unoccupied cation d states. We also explain the variations, along the series, of

the individual contributions to Z^* arising from the occupied band manifolds.

PACS numbers: 71.25.Tn, 77.22.Ej, 77.84.Bw

Typeset using REVTEX

The dynamical charges (also called Born effective charges or transverse charges) measure the macroscopic polarization induced by relative sublattice displacements in a polar insulator. When the ionic material is partly covalent, the dynamical charges present nontrivial features: the displacement of a given ion induces a substantially nonrigid displacement of the associated electronic charge. This case includes oxides, which have received recently attention from different groups. Apparently similar oxides have strikingly different behavior: some (like the ferroelectric perovskites) have giant dynamical charges,[1,2] while others (like ZnO) display dynamical charges close to the nominal static ones.[3] The present work addresses the series of the alkaline–earth oxides MgO, CaO, SrO, and BaO. They have the rocksalt structure, and therefore the anion and cation Born tensors are diagonal, with opposite values of the charges. Their dynamical charges Z^* show experimentally a well defined trend in their deviation from the nominal value of the rigid–ion picture, *i.e.* $+2$ (cation) and -2 (anion) in units of the elementary charge, which will be used throughout. Lattice–dynamical measurements of the LO-TO splitting at the Brillouin-zone center allow an accurate determination of $|Z^*|^2/\varepsilon_\infty$, where ε_∞ is the electronic ("static–high–frequency") dielectric constant and is the major source of uncertainty when comparing theory with experiment. For MgO, the observed Z^* is nearly nominal; in the heavier oxides Z^* increases monotonically along the series, up to the value 2.7–3.0 in BaO. In the present theoretical study we investigate such a trend, focussing in particular on the individual contributions due—in each material—to different groups of occupied bands. As an additonal tool, we also perform computational experiments on "fake" materials, where the strength of covalence has been artificially reduced.

The macroscopic polarization induced by a given sublattice displacement in polar dielectrics is related to the integrated macroscopic current traversing the sample. From a theoretical standpoint, reasoning in terms of *currents*—as opposite to *charges*—provides bulk quantities which are well defined in the thermodynamic limit and solves many of the problems which have plagued the polarization concept until recently.[4,5] The Born dynamical–charge tensors measure the relationship between sublattice displacements and the corresponding

macroscopic electric fields. The Born charge of a given ion is also defined as the second derivative, with respect to the field and to the displacement, of a suitable thermodynamic potential (see e.g. Ref. 5, Sec. VIII). As such, Z^* measures the linear polarization induced in zero field by a unit sublattice displacement, or equivalently the linear force induced by a unit field upon a given ion, at zero displacement. The modern theory of the macroscopic polarization—implemented in the present study with first–principles methods—allows one to calculate Born charges as Berry phases.[4,5]

All our calculations are semirelativistic and use the self–consistent full–potential linearized–augmented–plane–wave (FLAPW) method.[6] The local–density approximation (LDA) to the density functional theory with the Hedin–Lundqvist exchange and correlation potential has been used. Through this study, we have used the experimental lattice constants of the materials, whose values in a.u. are 7.97 (MgO), 9.09 (CaO), 9.75 (SrO), and 10.46 (BaO). In the following, we will indicate generically as MO any one of these four oxides.

The accurate evaluation of the MO wavefunctions, as required in the calculation of Berry phases,[4,5] is a challenge for all band structure methods, including pseudopotentials, because of the large energy range that must be spanned by the basis functions. All occupied states ranging from cation M np (Mg: n=2; Ca: n=3; Sr: n=4; Ba: n=5) and oxygen 2s up to oxygen 2p have *a priori* to be retained, leading, *e.g.*, to an energy range of 39 eV for MgO. Specific to the LAPW method is the fact that O 2p tails extending inside the cation muffin–tin spheres have to be described very accurately. This is a difficult task in the standard LAPW method because linearization is performed around M ns and M np energies inside cation spheres, *i.e.* much below the relevant O 2p energies. Using two energy windows with different linearization energies and diagonalizations in each window doesn't solve entirely the problem. Indeed, explicit interwindow orthogonalization is usually not implemented in the computer programs, and non–orthogonality effects corrupt substantially the overlap matrices required for the Berry phase calculation. One way to circumvent these difficulties is to expand the usual LAPW basis set with local orbitals.[7] Mutual state orthogonality is

then enforced, and variational freedom is increased. An alternative way, consists simply of shrinking the cation sphere until the largest part of the O $2p$ orbitals is in the O spheres and in the interstitial region. A standard one–window LAPW calculation is then performed, with an increased cutoff in reciprocal space corresponding to the shrinking of the cation sphere. We have used the latter approach in our study, keeping the oxygen sphere radius fixed to the value of 1.8 a.u. The above criteria for the cation spheres lead to the values 1.1, 1.6, 1.9, and 2.3 a.u. for the Mg, Ca, Sr, and Ba sphere radii, respectively. We have checked that results are in good agreement with those obtained from the LAPW/local–orbital method and the larger values of the cation radii (1.5 a.u. in the case of MgO).

We show in Fig. 1a the electronic energy bands of MgO, and in Fig. 2 those of the other materials. Several features of the band structures have some relevance to the analysis of the dynamical charges, and therefore we pause to scrutinize them in some detail.

Starting with the O $2s$ band, we notice that its center is about 15 eV below the edge of the O $2p$ valence bands in all four materials. This finding agrees with experiment though the magnitude is less than the measured one,[8] 18–21 eV, as a consequence of the well known deficiencies of LDA. By contrast, the position of the M np bands varies substantially. For MgO these bands are about 39 eV (to be compared with the experimental value[8] $\sim$ 46 eV) below the valence–band edge and are not visible in Fig. 1a. In CaO they appear at the bottom of the figure, in SrO they overlap with the O $2s$ band, and in BaO they are a few eV above it. This trend agrees with the experimental findings, despite smaller values of the energy separation from the valence edge. In all cases except MgO, while there is a non–negligible hybridization between O $2s$ and M np states, reaching a maximum in SrO, the band complex O $2s$ + M np scarcely interact with the remaining occupied states. We thus anticipate that the contribution to Z^* from this complex will be close to the nominal value, while the individual O $2s$ and M np contributions will deviate substantially.

There are also conspicuous conduction–band differences between MgO and the other oxides, which can be understood easily in terms of M nd states. For Mg (n=2), these states are absent and the gap is direct, whereas for n>2 they contribute significantly to the lowest

conduction bands, leading to an indirect gap at X. The lack of d states at low energy in MgO is also responsible for a lattice constant significantly smaller than in the other compounds. In order to separate a pure volume effect, we have performed an additional self–consistent band–structure calculation for MgO under a huge negative pressure, such that the lattice constant is increased up to that of CaO: these bands are shown in Fig. 1b. The energy gap decreases, the lowest conduction bands remain predominantly Mg $3s$, O $3s$, and O $3p$ and display a free–electron like behavior, while the highest O $2p$ valence bands flatten as a consequence of reduced interatomic interactions.

The three heaviest oxides have qualitively similar band structures, in particular the highest valence bands, and a gap which decreases along the series. The highest valence bands are nominally O $2p$, but inspection of the wavefunctions shows a partial d character (about one order of magnitude larger than in MgO), hence a sizeable bonding with the M nd orbitals which determine the conduction band minimum at X.

In the following, we will study the dynamical charge $Z^*_{\rm O}$ dragged by the displacement of an oxygen atom only. We have however explicitely verified that in our Berry phase calculation the acoustic sum rule $Z^*_{\rm M} + Z^*_{\rm O} = 0$ is fulfilled with great accuracy through the whole series. The results are reported in Table I and compared to experimental[9] data, whose range is due to uncertainty in the dielectric constant ε_∞. For the whole series the agreement of the theoretical results with the experimental ones is very good. Our results also agree with those of an ab–initio calculation for MgO, CaO, and SrO,[10] based on pseudopotentials and linear–response theory: notice that in this paper the Szigeti charges $Z^*_S = 3Z^*/\varepsilon_\infty$ are reported. For the heaviest compound, BaO, we have checked that inclusion of the spin–orbit coupling doesn't modify significantly the calculated value of $Z^*_{\rm O}$.

In our approach we can also calculate unambiguously the separate contributions to $Z^*_{\rm O}$ from different electronic states, whenever the corresponding bands are well separated in energy. Such a decomposition, performed previously in other materials,[2,3] is of paramount importance in identifying the physical mechanisms responsible for the deviations of Z^* from the nominal ionic values.

The oxygen $1s^2$ state can be safely considered as rigid, so the ionic core carries a charge of +6. In a completely ionic picture the electronic states $2s$ and $2p$ are fully occupied with eight electrons, thus providing the total nominal charge of -2. This oversimplified picture must be replaced, for real materials, by the values reported in Table I. The polarizable electronic states that can in principle contribute non trivial values, are M ns, M np, O $2s$, and O $2p$. For all materials, except SrO, the corresponding bands do not overlap with each other and their contribution can be computed separately. It is apparent in Table I that the M ns states, which are very deep in energy and localized in space, can be considered as rigid, *i.e.* the physics of the dynamical charge is in the behavior of the other three groups of bands.

Let us start with MgO, which behaves differently from the rest of the series. The O $2s$ states are rather far from any other electronic state, but nonetheless their share of dynamical charge is -2.21, larger than the nominal value. A similar peculiar feature of the O $2s$ states was found for other materials[2,3] but no satisfactory explanation of this finding has been proposed so far: therefore we scrutinize the issue in more depth here. First we notice that the Mg $2p$ states have a negligible contribution, as expected from their energy location. Secondly we notice that the O $2p$ states contribute less than the nominal value, in such a way that the effects of the only relevant bands (oxygen $2s$ and $2p$) add up to a total dynamical charge close to the nominal value. The reason for this is an appreciable interaction between O $2s$ and O $2p$ states, which we have identified by inspection of the relevant Bloch functions, and which is basically due to the short nearest–neighbor distance in MgO. We have further checked this by performing a separate calculation for a fake MgO, where we have added a repulsive potential, confined to the oxygen spheres, and acting only upon the radial s wavefunction. With a repulsive strength of 0.2 Ry, the $2s$ and $2p$ energy bands become closer in energy, and their partial contributions to $Z^*_{\rm O}$ become -2.25 ($2s$) and -5.82 ($2p$). The total value of $Z^*_{\rm O}$ is essentially identical for the fake and for the real material, which demonstrates our point. MgO is therefore a material where the occupied O $2s$ and O $2p$ orbitals interact amongst themselves, but scarcely with empty conduction states: when

oxygen is displaced, the strength of the O $2s$ − O $2p$ interaction is affected, but the subspace of the corresponding occupied bands remains about the same.

The other materials are—as expected—qualitatively different from MgO, and more similar amongst themselves. In agreement with the trends detected in the band structure analysis, the interaction of O $2s$ and M np states is significant, and results in a strongly non–nominal value of the partial charges associated with the corresponding bands. Looking first at the partial contribution due to O $2s$ states (in CaO and BaO) we notice a much larger deviation from the nominal value than in MgO. We understand this as the interaction with M np bands; in addition, there is an interaction with O $2p$ states, similar to the one occurring in MgO, although much weaker. However, in the three heavier materials, the O $2s$ and M np contributions add up to an almost nominal value: -2.09 in CaO, -2.06 in SrO, and -1.98 in BaO. Therefore, the deviation of $Z^*_{\rm O}$ from the nominal value is due to the partial contribution of the highest occupied bands, which are O $2p$ with substantial bonding to cation nd states. The phenomenon here is then qualitatively similar to—although quantitatively less spectacular than—the one we have discovered previously[1,2] in ferroelectric $KNbO_3$.

In order to substantiate this claim, we have performed a series of calculations on fake materials, where the bonding of O $2p$ states with cation nd states is artificially suppressed by adding a repulsive potential, confined to the cation sphere, and acting only upon the d radial wavefunctions. The unoccupied nd states are then pushed higher in energy. The calculated effective charges, for the whole series of fake materials, are reported in Table II. As expected, our modification of the potential has no effect on the calculated Z^* of MgO; instead the effects are quite relevant for the other three cases, where the values of Z^* are much closer to the nominal ionic charges than in the real materials. Almost all partial contributions change conspicuously, not only those corresponding to states closest to the fundamental gap, since the fake repulsive potential affects the lowest bands as well. However, the partial variations corresponding to low lying states are unimportant, since they are due to intermixing of occupied states amongst themselves. In this respect the situation is the

same for the fake crystals as for the real ones: the sum of the O 2s and M np contributions adds up to an almost nominal value. The only important variation is in the contribution of the O 2p electronic states, which can no longer interact with the lowest conduction states, thus resulting in a near–nominal value of the dynamical charges.

Finally, we note an heuristic trend in the partial contributions given in Tables I and II, as well as those available in the literature for the dynamical charges.[2,3] In the case of an anion displacement, when p states interact with s (d) states, the deviations from the nominal value of the partial contributions to Z^* are positive (negative) for p states, and negative (positive) for s (d) states. In the case of a cation displacement, the above effects are opposite. This rule controls also the total value Z^* of the three heaviest oxides, where the only relevant interaction is the one between the highest valence states (predominantly O 2p–like) and d–like conduction states.

We thank N. Binggeli for her interest in this work. We are also grateful to D. Singh for helpful discussions concerning the local–orbital method. This work was supported by the Swiss National Science Foundation grant 20–39.528.93. H.K acknowledges support by NSF grant DMR-9404954, and R.R acknowledges partial support by ONR grant N00014-96-1-0689. Calculations have been performed on the computers of EPF–Lausanne and ETH–Zürich and the Cornell Theory Center.

REFERENCES

[†] Also at Institut Romand de Recherche Numérique en Physique des Matériaux (IRRMA), PHB Ecublens, CH–1015 Lausanne, Switzerland.

[1] R. Resta, M. Posternak, and A. Baldereschi, Phys. Rev. Lett. **70**, 1010 (1993); M. Posternak, R. Resta, and A. Baldereschi, Phys. Rev. B **50**, 8911 (1994).

[2] Ph. Ghosez, X. Gonze, Ph. Lambin, and J.–P. Michenaud, Phys. Rev. B **51**, 6765 (1995).

[3] S. Massidda, R. Resta, M. Posternak, and A. Baldereschi, Phys. Rev. B **52**, 16977 (1995).

[4] R. Resta, Ferroelectrics **136**, 51 (1992); R.D. King–Smith and D. Vanderbilt, Phys. Rev. B **47**, 1651 (1993); R. Resta, Europhys. Lett. **22**, 133 (1993).

[5] R. Resta, Rev. Mod. Phys. **66**, 809 (1994).

[6] H.J.F. Jansen and A.J. Freeman, Phys. Rev. B. **30**, 561 (1984); S.H. Wei and H. Krakauer, Phys. Rev. Lett. **55**, 1200 (1985).

[7] D. Singh, Phys. Rev. B **43**, 6388 (1991).

[8] S.P. Kowalczyk *et al.*, Solid State Commun. **23**, 161 (1977); H. van Doveren and J.A.Th. Verhoeven, J. Elect. Spect. Relat. Phen. **21**, 265 (1980); L. Fiermans *et al.*, Phys. Status Solidi a **59**, 569 (1980).

[9] *Zahlenwerte und Funktionen aus Naturwissenschaften und Technik*, edited by O. Madelung, Landolt-Börnstein, New Series, Group III, Vol. 17b (Springer, New York, 1982).

[10] O. Schütt, P. Pavone, W. Windl, K. Karch, and D. Strauch, Phys. Rev. B. **50**, 3746 (1994).

FIGURES

FIG. 1. Energy bands of MgO calculated (a) at the experimental value a=7.97 a.u. of the lattice parameter and (b) under negative pressure, corresponding to a=9.09 a.u. as in CaO.

FIG. 2. Energy bands of (a) CaO, (b) SrO, and (c) BaO calculated at the experimental value of the lattice constant.

TABLES

TABLE I. Decomposition of the Born dynamical charge $Z^*_{\rm O}$ of oxygen for the series of alkaline–earth oxides into contributions from different groups of bands and from the ionic cores. For SrO, the contributions from O $2s$ and Sr $4p$ cannot be separated; their sum is -2.06. The nominal values, in a completely ionic picture, are given in brackets.

	MgO	CaO	SrO	BaO
M ns [0.0]	-0.02	-0.01	-0.01	$+0.00$
O $2s$ [-2.0]	-2.21	-2.68		-2.72
M np [0.0]	$+0.01$	$+0.59$		$+0.74$
O $2p$ [-6.0]	-5.85	-6.35	-6.46	-6.82
Core [+6.0]	$+6.00$	$+6.00$	$+6.00$	$+6.00$
Total [-2.0]	-2.07	-2.45	-2.53	-2.80
$Z^*_{\rm O}$ Expt.[a]	1.96/2.02	2.26/2.30	2.34/2.47	2.69/2.97

[a]From Ref. 9

TABLE II. Same as in Table I, but with a fake repulsive potential acting, within the cation sphere only, on the d–like component of the electronic states. For SrO, the sum of the O $2s$ and Sr $4p$ contributions is -2.02

	MgO	CaO	SrO	BaO
M ns	-0.03	-0.04	-0.04	-0.05
O $2s$	-2.22	-2.37		-3.03
M np	$+0.02$	$+0.32$		$+1.07$
O $2p$	-5.83	-5.91	-6.03	-6.25
Core	$+6.00$	$+6.00$	$+6.00$	$+6.00$
Total	-2.06	-2.00	-2.09	-2.26

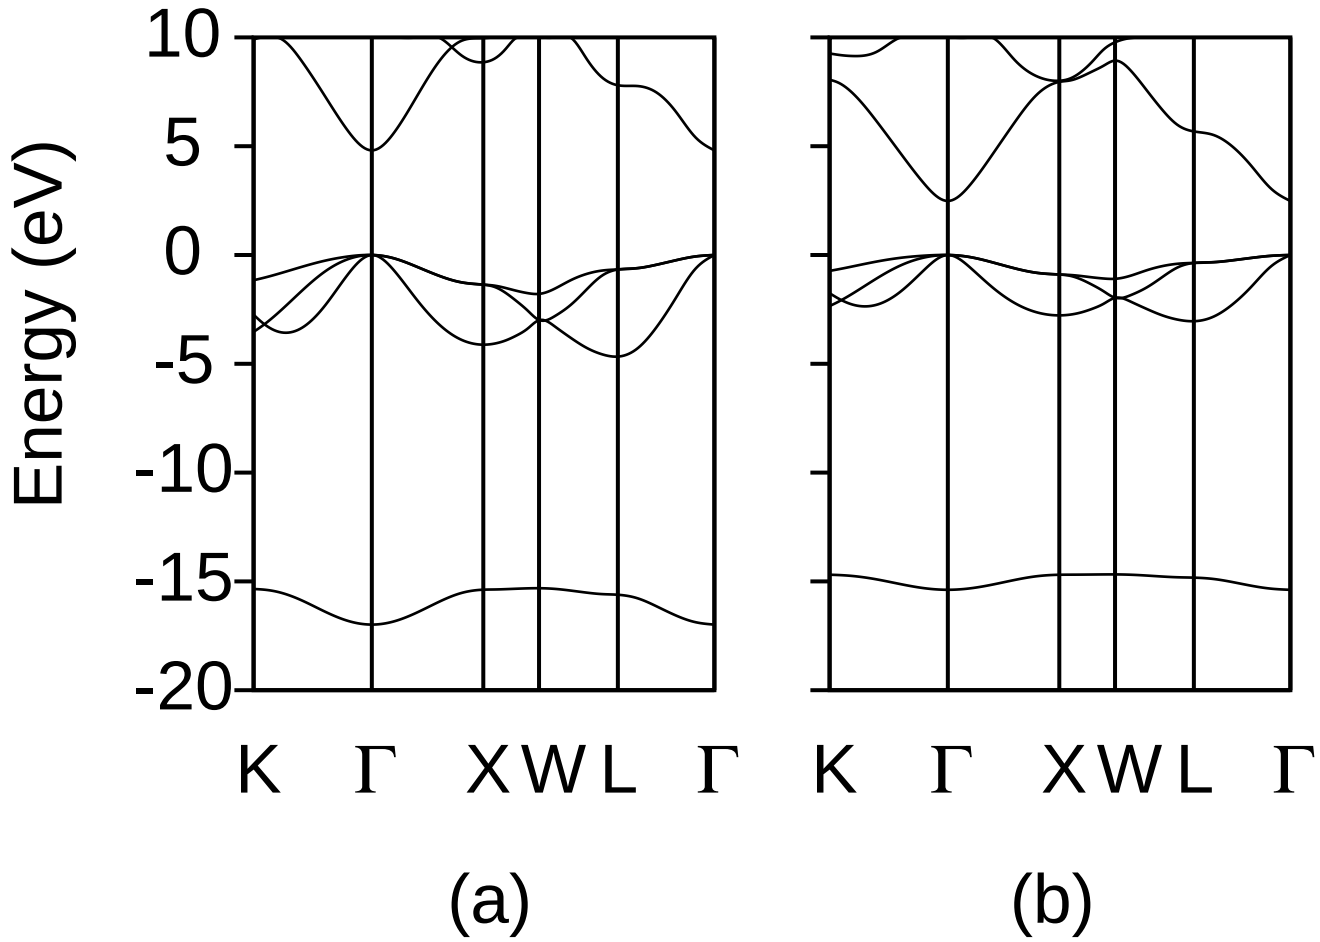

Figure 1, Posternak et al, Phys. Rev. B15

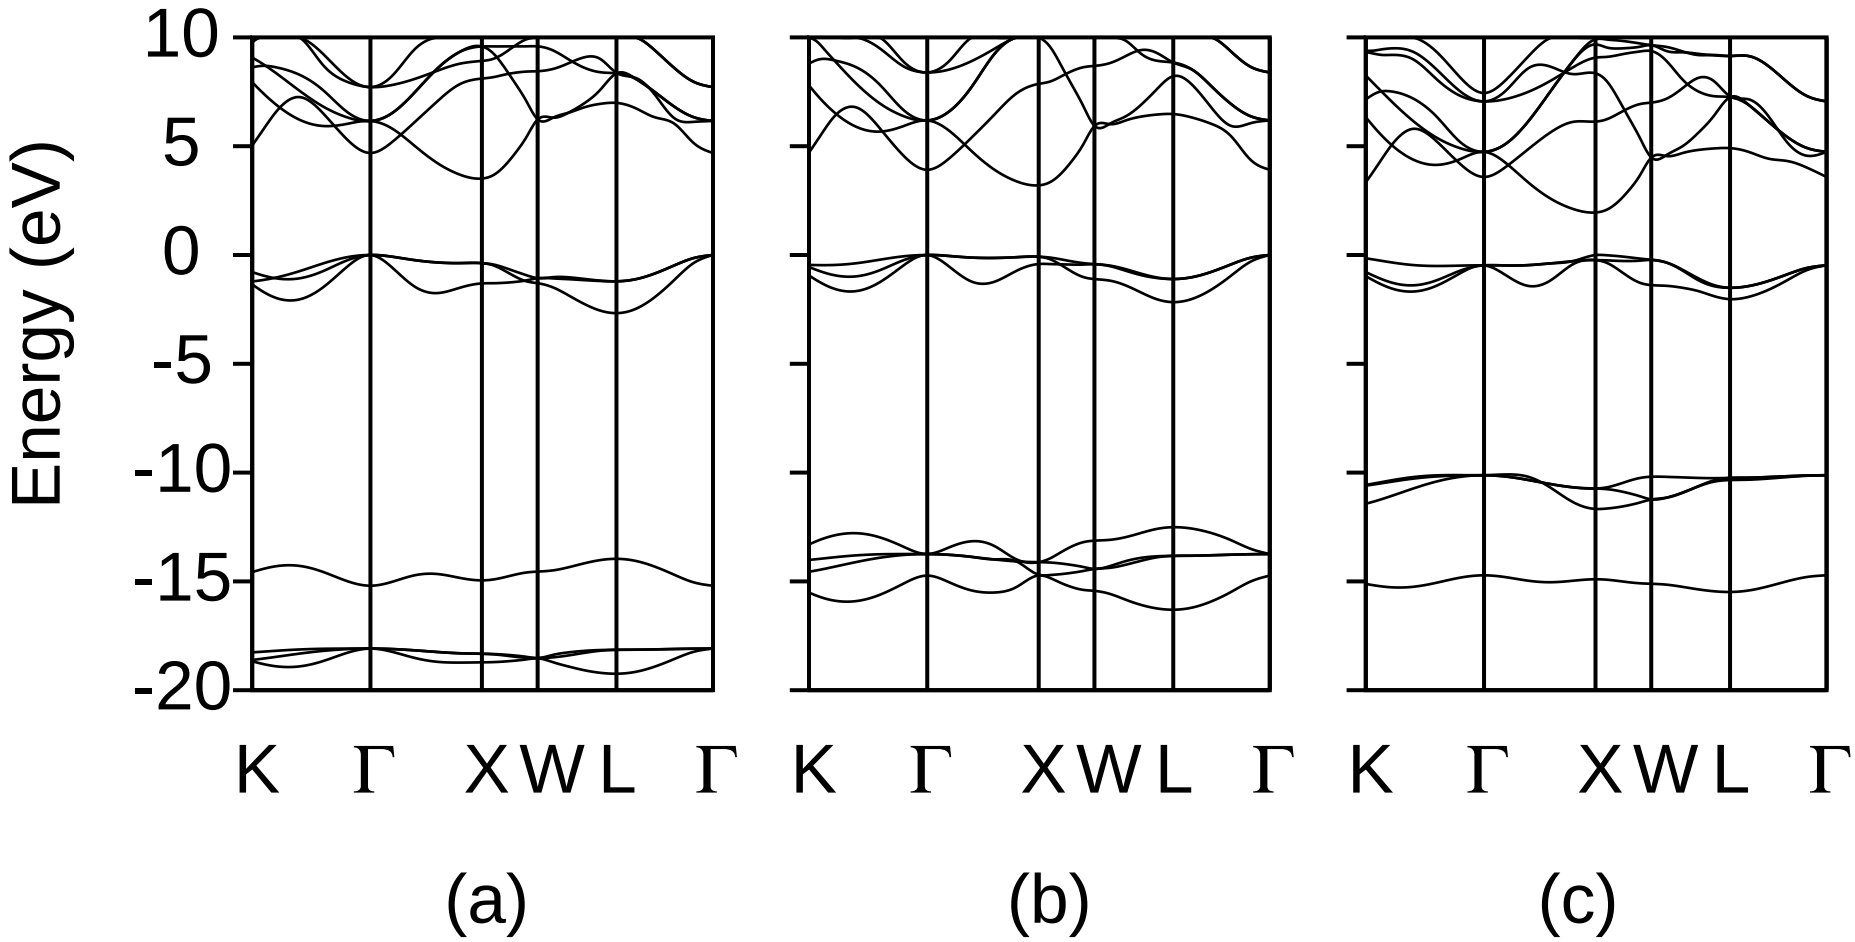

Figure 2, Posternak et al, Phys. Rev. B15